

AN1232 Application note

Ruggedness improvement of RF DMOS devices

Introduction

RF amplifiers often experience impedance mismatch between output and load. Such an impedance mismatch generates a reflected wave towards the RF power transistor, making a much more stringent working environment for the transistor. Working conditions grow critical when the load is disconnected from the output of the RF power transistor, since, in this case, the reflected wave amplitude becomes comparable to the incident one.


RF transistors are able to withstand severe impedance mismatch conditions particularly essential for applications such as plasma generators or nuclear magnetic resonators which operate under rough conditions. DMOS devices used in such applications appeared to lack the necessary ruggedness when operating under severe RF load mismatch conditions. This weakness was believed to be intrinsic.

Based on the need to improve the ruggedness of RF power DMOS, an investigation was carried out and a theoretical model simulating the failure mode mechanism was developed. Finally, relevant corrective actions were undertaken.

Proposed model AN1232

1 Proposed model

Figure 1. Npn Bipolar parasitic transistor

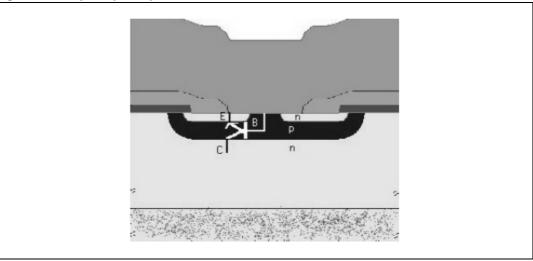

Under impedance mismatch conditions the RF power transistor is subjected to a reflected wave with an amplitude that cannot be controlled and, in the worse case, with a voltage value that can exceed the BV_{dss} of the device itself. Hence, the DMOS works as a voltage clamp for this wave. Under such conditions the device is subjected to an electric current whose amplitude is proportional to the power of the incident wave. Simultaneously, the DMOS experiences a temperature rise proportional to the duration, voltage swing (BV_{dss}) and amplitude of the above current. In the DMOS cross section, shown in *Figure 1*, the presence of an npn bipolar parasitic transistor, in which the base and emitter are shorted by means of the DMOS source metallization, are clearly noticeable.

Under static conditions the parasitic transistor is inhibited by the short circuit, but under dynamic conditions, when the reverse breakdown current flows through the device, the short circuit condition itself is modified. In fact, this current crosses the base-emitter junction through the base resistance which is increased by the depletion layer due to the reverse voltage. This results in a variation in V_{be} .

We can assume that:

Equation 1

$$V_{be} = R_{be} \bullet I_{dis}$$


If I_{dis} (base distributed current) and R_{be} (base distributed resistance) are large enough, the potential on the emitter side opposed to the short circuit is sufficient to turn on the bipolar transistor, thus concentrating the current and destroying the device.

A simplified model was developed (see *Figure 2*) to simulate the mismatch condition on the drain of the DMOS by means of the inductance L.

5/

AN1232 Proposed model

Figure 2. Mismatch condition model

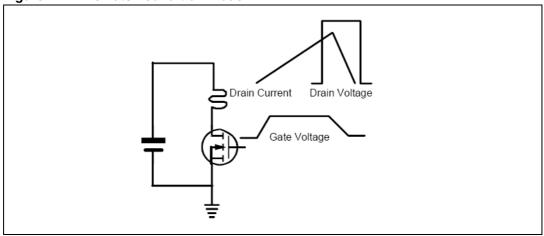

During the turnoff period the device is in breakdown condition and subjected to the current induced by the inductance, thus the device dissipates power. Of course, depending on the turnoff duration, we have to distinguish between the turn-on of the parasitic transistor and the thermal derating, with relevant operations out of the reverse safe operating area of the DMOS. In fact, during such operations it is possible that the device exceeds the maximum allowed junction temperature (200 $^{\circ}$ C). In the case of load mismatch, however, the value of the inductance is far from causing a thermal overstress. Therefore, a turn-on due to R_{be} is far more likely to happen.

Another occurrence is when the voltage, due to the reflected wave, is applied on the drain of the DMOS at zero current. In this case the capacitance of the body-drain junction is involved. This capacitance suddenly changes value due to the changed potential, hence making a current whose value is given by:

Equation 2

$$I_{dis} = C_{bd} \cdot \frac{dV}{dt}$$

this together with *Equation 1* gives:

Equation 3

$$V_{be} = R_{be} \cdot C_{bd} \cdot \frac{dV}{dt}$$

Therefore, one can see that even a zero current switching condition can cause the turn-on of the parasitic transistor.


Actions AN1232

2 Actions

In order to validate the model several tests were performed. The failure current was measured during a UIS (Unclamped Inductive Switching) test. In particular the failure current density was also tested. Results are listed in *Table 1*.

In a typical DMOS structure the body acts as the base of the parasitic transistor while the source behaves as the emitter. The $R_{\rm s}$ pinched values are typically in the KWs range. By using the existing diffusion processes it is not possible to change the body doping value in order to reduce either the DC gain ($h_{\rm fe}$) or the $R_{\rm be}$. This would have a dramatic impact on the DMOS threshold voltage. The only way to work on the parasitic transistor, without changing the characteristics of the DMOS, is to add a further doping level called deep-body doping. By doing so the $R_{\rm s}$ pinched is dramatically reduced to 100 ohm/square and the DC gain ($h_{\rm fe}$) of the parasitic transistor becomes close to one. This extra doping is implanted following the body doping process and prior to the body diffusion process. The Dmos structure is therefore modified as shown in *Figure 3*.

Figure 3. Deep body doping

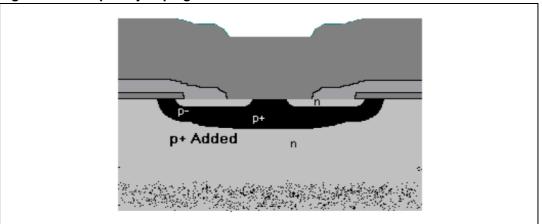

Since the deep body process is separated from the main body process (a further masking level and implant are required), typical DMOS parameters are unaffected. Optimum values for UIS and in VSWR can be obtained by using this structure and varying the deep body implant doses. Results from the test performed on the SD2921 device are listed in *Table 1*.

Table 1. UIS and VSWR output mismatch vs deep body dose

Deep body dose	UIS Failure (A)	VSWR
None	10	5:1
1e15	26	15:1
2e15	39	20:1
3e15	45	30:1

AN1232 Conclusion

3 Conclusion

We have demonstrated that DMOS ruggedness, under varying load mismatches, is dramatically improved with a single implant process through photoresist without modifying the DMOS layout. Also, RF power performances remain unaffected. From now on, deep body doping process will be applied to all products in the production phase.

VSWR, a characteristic ruggedness parameter for RF power transistors, is linked to the standard ruggedness parameters of the DMOS. Therefore, a UIS test, easily implemented and commonly applied in EWS (Electrical Wafer Sort), can give useful information on the ruggedness of RF power devices.

4 Revision history

Table 2. Revision history

Date	Revision	Changes	
21-Jun-2004	12	Minor text changes	
30-Jul-2007	13	The document has been reformatted	

Please Read Carefully:

Information in this document is provided solely in connection with ST products. STMicroelectronics NV and its subsidiaries ("ST") reserve the right to make changes, corrections, modifications or improvements, to this document, and the products and services described herein at any time, without notice.

All ST products are sold pursuant to ST's terms and conditions of sale.

Purchasers are solely responsible for the choice, selection and use of the ST products and services described herein, and ST assumes no liability whatsoever relating to the choice, selection or use of the ST products and services described herein.

No license, express or implied, by estoppel or otherwise, to any intellectual property rights is granted under this document. If any part of this document refers to any third party products or services it shall not be deemed a license grant by ST for the use of such third party products or services, or any intellectual property contained therein or considered as a warranty covering the use in any manner whatsoever of such third party products or services or any intellectual property contained therein.

UNLESS OTHERWISE SET FORTH IN ST'S TERMS AND CONDITIONS OF SALE ST DISCLAIMS ANY EXPRESS OR IMPLIED WARRANTY WITH RESPECT TO THE USE AND/OR SALE OF ST PRODUCTS INCLUDING WITHOUT LIMITATION IMPLIED WARRANTIES OF MERCHANTABILITY, FITNESS FOR A PARTICULAR PURPOSE (AND THEIR EQUIVALENTS UNDER THE LAWS OF ANY JURISDICTION), OR INFRINGEMENT OF ANY PATENT, COPYRIGHT OR OTHER INTELLECTUAL PROPERTY RIGHT.

UNLESS EXPRESSLY APPROVED IN WRITING BY AN AUTHORIZED ST REPRESENTATIVE, ST PRODUCTS ARE NOT RECOMMENDED, AUTHORIZED OR WARRANTED FOR USE IN MILITARY, AIR CRAFT, SPACE, LIFE SAVING, OR LIFE SUSTAINING APPLICATIONS, NOR IN PRODUCTS OR SYSTEMS WHERE FAILURE OR MALFUNCTION MAY RESULT IN PERSONAL INJURY, DEATH, OR SEVERE PROPERTY OR ENVIRONMENTAL DAMAGE. ST PRODUCTS WHICH ARE NOT SPECIFIED AS "AUTOMOTIVE GRADE" MAY ONLY BE USED IN AUTOMOTIVE APPLICATIONS AT USER'S OWN RISK.

Resale of ST products with provisions different from the statements and/or technical features set forth in this document shall immediately void any warranty granted by ST for the ST product or service described herein and shall not create or extend in any manner whatsoever, any liability of ST.

ST and the ST logo are trademarks or registered trademarks of ST in various countries.

Information in this document supersedes and replaces all information previously supplied.

The ST logo is a registered trademark of STMicroelectronics. All other names are the property of their respective owners.

© 2007 STMicroelectronics - All rights reserved

STMicroelectronics group of companies

Australia - Belgium - Brazil - Canada - China - Czech Republic - Finland - France - Germany - Hong Kong - India - Israel - Italy - Japan - Malaysia - Malta - Morocco - Singapore - Spain - Sweden - Switzerland - United Kingdom - United States of America

www.st.com

577